

Hemicellulose biorefineries: a review on biomass pretreatments

Florbela Carvalheiro, Luís C. Duarte and Francisco M Gírio*

INETI, Departamento de Biotecnologia, Unidade de Fisiologia Microbiana e Bioprocessos,
Estrada do Paço do Lumiar, 22, 1649-038, Lisboa, Portugal

Received 15 July 2008; revised 20 August 2008; accepted 03 October 2008

Biomass pretreatment (BP) plays a crucial role in a lignocellulose feedstock-based biorefinery (LCFBR) for processing of three major output streams (cellulose, hemicelluloses and lignin) into chemicals and biofuels. BP includes processing of lignocellulosic material (LCM) under aqueous, dilute acid or alkaline media to obtain a cellulosic fraction, which is then fermented to produce bioethanol. Hemicellulose is usually treated as a secondary stream due to lack of efficient fermentation of hemicellulosic sugars to ethanol. This review provides BPs assuming that hemicellulose stream should be integrated in LCFBR as a primary fraction for converting into value-added compounds other than bioethanol. Different LCM treatments are analyzed foreseeing bio-based products possible to obtain from hemicellulose path.

Keywords: Bioethanol, Biorefineries, Hemicellulose, Lignocellulosic biomass, Pretreatments

Introduction

Biomass pretreatments (BPs) technologies¹⁻⁴ (chemical, physical or biological) change/remove structural and compositional constraints to improve hydrolysis rate and increase yields of fermentable sugars from cellulose. Therefore, BPs can be divided in two groups: i) Those related to chemical and biochemical constraints such as cellulose recovery, digestibility, by-product/inhibitor formation; and ii) Those related to bioprocess costs, such as, water usage and energy efficiency. This paper reviews main advantages and bottlenecks of currently available BP technologies, Ne:foreseeing potential added-value products possible to be obtained and most relevant factors, which influence both product yield and consistency.

Biorefinery Concept

Biorefinery is an overall concept of an integrated and diversified processing plant where biomass feedstocks are converted into a wide range of valuable products, much likewise to petroleum refineries. Integrated biorefinery is a processing facility that extracts

carbohydrates, oils, lignin, and other materials from biomass, converts them into fuels, high value chemicals and other materials, with a zero waste approach⁵⁻¹⁰ (Fig. 1). Pulp and paper mills, corn wet and dry mills that produce multiple products from biomass can be categorized as biorefineries. At Mediterranean countries, including Portugal, olive-pomace oil extraction facilities and wine distilleries are examples of *proto-biorefineries* since they produce a wide combination of food, feed and power¹¹.

In comparison to petroleum refineries, biorefineries utilize a variety of feedstocks and a larger range of processing technologies. Biomass feedstock is bulkier than fossil fuels¹². By integrating production of higher value bioproducts into biorefinery's fuel and power output, overall profitability and productivity of all energy related products are potentially improved. Increased productivity and efficiency can also be achieved through operations that decrease overall energy intensity of biorefinery's unit operations, maximizing use of all feedstock components, byproducts and waste streams, and using scale-up economies, common processing operations, materials, and equipment to drive down all production costs^{5,7}. Biorefinery can be considered as an evolution of concepts like "*Green Chemistry*" or *Chemurgy*^{6,13}.

*Author for correspondence

Tel: +351 21 092 4721; Fax: +351 21 716 36 36

E-mail: francisco.girio@ineti.pt

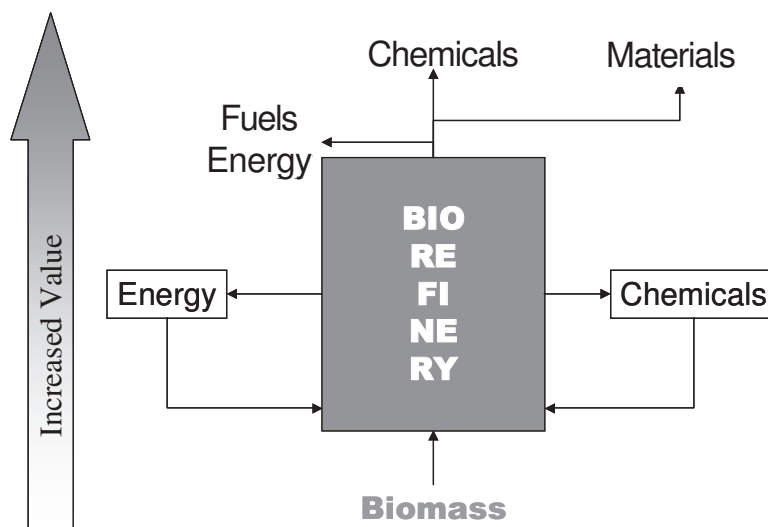


Fig. 1—Biorefinery concept

Biorefinery Platforms

Depending on raw materials, technological processes, and products obtained, biorefinery platforms can be distinguished (Table 1) based on sugar (biochemical), syngas (thermochemical), biogas, or carbon-rich chains platforms⁷. Biorefinery platforms may incorporate other processes from other platforms¹⁴ (anaerobic digestion of fermentation effluents¹⁵, or thermochemical transformation of lignin in sugar platform biorefinery). Biorefinery platforms, based only on main raw materials^{6,8,16} used, are: i) Lignocellulose feedstock-based biorefinery (LCFBR) that uses nature-dry raw material (wood, straw etc.); ii) Whole crop biorefinery that uses cereals; and iii) Green biorefineries that use nature-wet biomasses such as green grass, alfalfa, immature cereal etc.

Biochemical and Thermochemical Biorefineries

Most promising emerging biorefinery platforms are sugar (biochemical) and syngas (thermochemical) platforms⁷. Biochemical platform focuses on fermentation of sugars extracted from lignocellulosic feedstocks. After feedstock preparation (size reduction), conversion technologies involve three basic steps: i) Convert biomass to sugar or other fermentation feedstock; ii) Bioconversion of these biomass intermediates using biocatalysts; and iii) Process products to yield added value chemicals, fuel-grade ethanol and other fuels, heat and/or electricity. Top value added chemicals that can be produced in a biochemical platform biorefinery have been identified⁵ (Table 2). Economic viability of a biochemical biorefinery is highly

sensitive to feedstock cost, operating scale and macromolecular biomass composition.
















Thermochemical biorefineries focuses on gasification (heating biomass with about one-third of oxygen necessary for complete combustion, producing syngas), and/or pyrolysis (heating biomass in absence of oxygen, producing a pyrolysis oil). Both syngas and pyrolysis oil can be used as cleaner and more efficient fuels than solid biomass, but can also be chemically converted to other valuable fuels and chemicals. After feedstock preparation (drying, size reduction), conversion technologies include feeding, conversion (gasification, pyrolysis), and product clean up and conditioning. Hydrogen and methanol are probably the best short-term options for several biobased commodity chemical production since obtaining simple alcohols, aldehydes, mixed alcohols and Fischer-Tropsch liquids from biomass are not economically viable. Gas cleanliness is key barrier to economic production of syngas from biomass⁵. Economic viability of this type of biorefinery is also highly sensitive to feedstock cost and operating scale, but conversely to biochemical platform, macromolecular biomass composition does not play such an important role².

Although biochemical platforms costs can be lower than thermochemical platforms, at least in short to mid-term, there is not yet a clear definition of what is the most appropriate capacity for a biochemical biorefinery. Some studies pointed out to values close to or higher than 350,000 t/y dry feedstock for ethanol-based biorefineries^{15,17,18} and a supply region up to 150 km radius¹⁹. But, if whole material could be upgraded for

Table 1—Most common biorefinery platforms and their major characteristics

Platform	Raw materials	Main processes	Products	Development stage
Sugar (Biochemical)	Lignocellulosic and starch biomass	Chemical and enzymatic hydrolysis, Fermentation, Biotransformation, Chemical and catalytical processes	Added value chemicals (both from sugar and lignin) Building block chemicals Materials (from lignin or lignocellulose) Fuel ethanol. Heat and electricity (from lignin)	Laboratory, large scale pilot plant and commercial (sugarcane and starch based)
Syngas (Thermochemical)	Lignocellulosic biomass but also plastics, rubber etc.	Thermochemical processes : - Gasification - Pyrolysis	Syngas Pyrolysis oil Added value chemicals Gaseous or liquid fuels	Laboratory, large scale pilot plant
Biogas	Liquid effluents Manure	Anaerobic digestion	Methane and carbon dioxide (biogas) Added value chemicals	Large scale pilot plant, commercial
Carbon-rich chains (Oil)	Plant oils such as soybean, rapeseed corn, palm, and canola oils. Animal fat	Transesterification	Fatty acid methyl ester (biodiesel), Glycerin and fatty acids as platform chemicals	Commercial

Table 2—Top value added chemicals derived from sugars in a biochemical biorefinery platform⁵

	Aminoacids	Carboxylic acids	Polyols	Lactones
C3		3-Hydroxy propionic acid 	Glycerol 	
C4	Aspartic acid 	Succinic acid  Fumaric acid  Malic acid 		3-Hydroxy butyrolactone 
C5	Glutamic acid 	Itaconic acid  Levulinic acid 	Arabitol  Xylitol 	
C6		Glucaric acid  2,5 furan dicarboxylic acid 	Sorbitol 	

several high value co-products (hemicellulose and lignin fractions), total capacity to ensure economic viability can decrease to 33,000 t/y²⁰, which opens very interesting opportunities to upgrade local agro-industrial byproducts^{11,21}. Although biochemical platform is in a more advanced stage as compared to other biorefinery platforms, many improvements²²⁻²⁷ are still needed.

Pretreatment Processes

Depending on the process and conditions used, during pretreatment, hemicellulose sugars may be degraded to weak acids, furan derivatives and phenolics²⁸. These compounds may inhibit the later fermentation processes, leading to lower yields and productivities.

Acid Hydrolysis

Acid catalyzed hydrolysis have been described as early as 19th-century, with commercial applications from beginning of 20th century^{6,29}. Acid hydrolysis can be divided in two general approaches, based on concentrated acid/low temperature, or dilute acid/high temperature.

Concentrated Acid

Concentrated acid-based processes are very expensive² and cause significant operational problems^{4,29}. As a catalyst, sulphuric acid (H_2SO_4) is most commonly used although other mineral acids [hydrochloric (HCl), nitric (HNO_3) and trifluoroacetic acid (TFA)] have also been assayed. Concentrated acids remove mostly cellulose and hemicellulose, resulting in a lignin-enriched solid phase. Polysaccharide solubilization (soluble phase) is reached using different acid concentrations, like 72% H_2SO_4 , 41% HCl or 100% TFA³⁰. HCl and TFA are easier to recover than H_2SO_4 . Concentrated acids allow to operate at low/medium temperature and pressure leading to formation of low amounts of degradation products³¹. However, degradation products formation rate is severely affected by slight changes in temperature³², conversely what occurs in case of dilute acid hydrolysis even at high temperatures^{33,34}. Acid recovery is a key step for economic viability of concentrated acid pretreatments³⁵, and these neutralization costs have hampered general use of these pretreatments. Moreover, equipment corrosion problems are an additional disadvantage³⁶. Nevertheless, there seems to be a renewable interest in these processes³⁷.

Dilute Acid

Dilute sulfuric acid processes (0.5-1.5%, temp. 121-160°C) have been most favored for industrial application,

because it achieves reasonably high sugar yields from hemicellulose^{2,29}. H_2SO_4 is usual acid employed although HCl, HNO_3 , and H_3PO_4 are also employed^{3,36,38}. Compared to concentrated acid hydrolysis, this pretreatment generates lower degradation products as well much less corrosion problems in hydrolysis tanks, pipes, etc. Addition of CO_2 to aqueous solutions forms carbonic acid as an alternative of acid addition³⁹⁻⁴¹. Carbonic acid behaves better than most of inorganic acids and is specifically suited for hydrolysis conditions under mild pH at high temperatures and pressures⁴⁰. Although, carbonic acid is responsible for an increase in xylan hydrolysis, which is lignocellulosic material (LCM) dependent³⁹⁻⁴¹.

Based on studies of hemicellulose hydrolysis using percolation reactors⁴²⁻⁴⁴, novel technologies have been developed using counter-current shrinking-bed reactors⁴⁵, giving high cellulose hydrolysis yields without significant formation of degradation products⁴⁶. Besides inorganic acids, some weak organic acids, like maleic acid is a potential catalyst to promote cellulose hydrolysis^{47,48}.

Hydrothermal Pretreatments

Hydrothermal processes use water, steam or both, and heat for BP. Hydrothermolysis⁴⁹ started as a pretreatment method before enzymatic hydrolysis. Hydrothermal processes include autohydrolysis⁵⁰⁻⁵⁵, aqueous liquefaction⁵⁶, aqueous extraction⁵⁷, aqueous pretreatment^{58,59}, hydrothermolysis⁶⁰⁻⁶², aquasolv⁶³, hydrothermal pretreatment⁶⁴, aqueous pre-hydrolysis⁶⁵ and pressure cooking in water⁶⁶. Hydrothermal treatments mainly include liquid hot water (autohydrolysis) and steam-explosion between 150°C and 230°C⁶⁷. For temperatures below 100°C, there is no hydrolytic effect on material⁶⁸, whereas above 220°C some cellulose degradation takes place^{69,70}. Between 240-250°C, pyrolysis reactions become important^{71,72}. Reaction time of hydrothermal treatments varies from seconds to hours, which is related with operation temperature.

Solids concentration, usually reported as liquid-to-solid ratio (LSR), may vary between 2 and 100 (w/w)^{67,73}, although most common values are around 10. Higher LSR are usually associated to continuous reactors⁷³, whereas lower LSR are, in general, used in BPs that employ steam since specific heat of steam is higher than that of water. LSR may also affect catalyst (acid) concentration in reaction media by two way: i) Decrease of LSR lead to a higher release of acetyl groups favoring

depolymerization⁵⁰; and ii) Lowering LSR lead to increase in buffer capacity at a neutral pH, which mainly related with ash content of feedstock, decreasing hydrolysis rate^{74,75}.

Influence of particle size is not significant for high LSR, but for low LSR, increase of particle size leads to a decrease in biomass solubilization, probably due to a deficient LCM impregnation⁷⁶. For pretreatments requiring steam, influence of particle size seems to be more important, since for large biomass particles, joint effect slow heating time, that occurs in particle core, and short reaction times may lead to an irregular/heterogeneous biomass particle heating⁷⁷. For some LCM, particle size reduction is not necessary for occurring a maximal solubilization rate⁶³, while for other LCM similar size reduction clearly affects amount of solubilized polysaccharide recovered, indicating higher polymer degradation⁷⁸.

Autohydrolysis

Autohydrolysis process uses compressed liquid hot water (temp., 200°C; pressure, > saturation point;) to hydrolyze hemicellulose in minutes. Hemicellulose recovery is high, and no catalyst is needed in this process. Lignin is not significantly solubilized; neither sugar largely decomposes, thus yielding a liquid fraction without many potential bioconversion inhibitor compounds. However, solubilized hemicellulose appears mainly in oligosaccharide form^{55,79}.

Autohydrolysis/hydrothermal processes have a similar mechanism as dilute acid hydrolysis. Both are hydrolysis processes catalyzed by hydronium ions (H_3O^+). In autohydrolysis, where water is the only reactive added to substrate, catalysts of hydrolysis are in a first stage hydronium ions coming from water auto-ionization that lead to depolymerization of hemicelluloses by selective hydrolysis of both glycosidic linkages and acetyl groups. In a second stage, hydronium ions coming from acetic acid also act as catalysts, improving reaction kinetics. The contribution of hydronium ions from acetic acid is higher than that from water autoionization^{51,56}. Hydrolysis of uronic acids should also occur in first stages of treatment, simultaneously with acetyl groups⁸⁰. Despite to their resistance to hydrolysis⁸¹, uronic acids may also contribute to formation of hydronium ions⁶⁵ but their role in hydrolysis is still not completely understood.

In autohydrolysis⁸⁰⁻⁸³, acids resulting from hydrolysis of acetyl and uronic groups, originally present in hemicelluloses, catalyze hydrolysis of links between

hemicelluloses and lignin as well as hydrolysis of carbohydrates. Autohydrolysis may convert hemicelluloses into soluble saccharides with high yield and low byproducts formation^{57,63,84,85}, rendering a easily extractable⁵⁹ solid residue rich in cellulose and lignin. Owing to mild pH, corrosion problems are reduced^{57,68}, and steps of acid recycling and precipitates removal are no longer necessary. The possibility to reduce both capital and operational costs due to the absence of acid emphasizes both reduced environmental impact⁵⁹ and economical advantages of aqueous-based processes compared to other hydrolytic technologies⁸⁶. Autohydrolysis products are a mixture of oligosaccharides, monosaccharides, acetic acid and furan derivatives [furfural (2-furaldehyde) and hydroxymethylfurfural (5-hydroxymethyl-2-furaldehyde, HMF)], which can further undergo decomposition reactions, yielding formic acid⁸⁷ and levulinic acid⁸⁸, respectively.

Steam Explosion

Steam explosion was developed in 1925 for hardboard production⁸⁹. Use of steam explosion for BP was introduced in early 1980's on aspen wood⁹⁰. In this process, material is heated using high-pressure steam (20-50 bar, 210-290°C) for a short period (from seconds to few minutes). Steam condenses under high pressure, thereby "wetting" the material, which is driven out of reactor through a small nozzle by induced force. Several phenomena occur at this stage. Due to decrease in pressure, condensed moisture evaporates and desegregation of lignocellulosic matrix takes place, braking down inter- and intra-molecular linkages⁵¹. One study⁹¹ emphasized role of mechanical effects (shear and explosive decompression) in process efficiency, while other studies^{77,92} consider that explosive decompression is not essential for its efficiency. Other authors reported that process is fundamentally chemical in nature^{90,93}. Chornet & Overend⁹⁴ described steam explosion as being a thermomechanicochemical process where breakdown of structural components is aided by heat in the form of steam (thermo), shear forces due to expansion of moisture (mechano), and hydrolysis of glycosidic bonds (chemical).

There are several studies applying steam explosion for BP in ethanol process. Schultz *et al*⁹⁵ compared effectiveness of steam explosion pretreatment on mixed hardwood chips, rice hulls, corn stalks, and sugarcane bagasse. Steam explosion has also been used as a

pretreatment method for agricultural residues, namely *Onopordum nervosum* and *Cyanara cardunculus*⁹⁶, *Brassica carinata*⁹⁷, olive tree biomass⁹⁸, and sunflower stalks⁹⁹. Some steam explosion processes have been mostly used as pretreatment methods for kraft pulps bleaching in paper and pulp industry. Some well known steam explosion-based pretreatments reported include Masonite¹⁰⁰, Siropulper¹⁰¹, Iotech¹⁰² and STAKE (www.staketechnology.com) processes.

Most steam treatments yield high hemicellulose solubility (producing mainly oligosaccharides) along with low lignin solubility. Studies without added catalyst report sugars recoveries between 45-65%⁹³. Major operational difference between autohydrolysis and steam explosion processes is that in later higher temperatures along with shorter times are used, being also common the prior LCM impregnation with H_2SO_4 ^{71,77,103-107} or SO_2 ^{103,105-110}. A pretreatment variant of catalyzed steam explosion is CO_2 explosion³¹, which acts to steam and ammonia explosion³¹. Glucose yields in later enzymatic hydrolysis are low (75%) compared to steam and ammonia explosion. Overall, CO_2 explosion is more cost effective than ammonia explosion, preventing inhibitors formation^{2,4}.

Wet Oxidation

In wet oxidation, autohydrolysis occurs in presence of oxygen or air as catalysts¹¹¹, which allows reactor operation at reduced temperatures and to shorter reaction times. On the other hand, pretreatment is more expensive mainly due to capital costs associated with pressure equipment. However, Na_2CO_3 ¹¹² and not oxygen is the most employed catalyst for wet oxidation pretreatments. Under alkaline medium, it is possible to get high rates of biomass-to-monosaccharides under moderated conditions, short reactions time and low formation of furan aldehydes^{112,113} and phenolics aldehydes, but not aliphatic acids^{113,114}. During wet oxidation, occurrence of considerable delignification^{112,113}, is correlated with the increase of carboxylic acids¹¹³.

Delignification Pretreatments

Delignification methods, mostly employed in pulp and paper kraft and sulphite technologies, discharge huge amount of liquid and gaseous wastes such as sulfur-containing gas emissions. Alternative delignification methods include organosolv treatments where lignin removal is promoted by direct action of an organic solvent (ethanol, methanol, acetone, acetic acid, formic acid, ethyl acetate, etc.) to solubilize lignin and hydrolyze

hemicellulosic fraction³¹. When a catalyst is used (acids, anthraquinone or salts), a more selective delignification can be reached and lignin itself is less degraded and of higher added-value for further technical applications^{115,116} (www.lignol-innovations.com). Lignol approach¹¹⁷ uses a blend of ethanol and water (50:50, w/w), at 200°C and 400 psi, to extract from LCM most of lignin as a fine precipitate by flashing pulping liquor to atmospheric pressure, followed by rapid dilution with water. Water-soluble stream yield hemicellulose sugars (50% in oligomeric form), besides significant amounts of furfural. Biodelignification (biological degradation of lignin by microorganisms) has advantages of low energy use and mild environmental conditions but hydrolysis rate is very low⁴. Sometimes biological treatments are used in combination with chemical treatments².

Alkaline Treatments

Alkali pretreatment increases cellulose digestibility. Depending on catalyst used, alkaline pretreatments can be divided into two major groups: i) Pretreatments that use sodium, potassium, or calcium hydroxide; and ii) Pretreatments that use ammonia. Conversely to acid or hydrothermal processes, alkaline-based methods are more effective for lignin solubilization exhibiting only minor cellulose and hemicellulose solubilization, excepting ammonia recycling percolation treatment, which yield biomass solids mostly containing cellulose^{2,4,118}.

Lime and NaOH Pretreatments

Sodium and calcium hydroxide (lime) are most common catalysts (conc. 0.05-0.15 g alkali/g biomass) applied in batch mode directly to biomass¹¹⁹⁻¹²⁴, or as a subsequent treatment to acid hydrolyzed biomass^{125,126}. Use of alkali treatment (temp., 30-130°C; reaction time, 10 min - 18 h) before an acid hydrolysis has also been reported¹²⁷. As a possible way to increase efficiency, ultrasonically assisted extraction has been reported to give a slightly higher yield of hemicelluloses and specially of lignin, than those of classical alkali procedure¹²⁸. From the obtained hydrolyzates, it is possible to easily recover phenolic compounds (ferulic and *p*-coumaric acids from brewery's spent grain) for applications in food, health, cosmetic, and pharmaceutical industries^{121,129}. Depending on feedstock and operating conditions, significant increases on glucose recovery are reported from 60% to almost quantitative glucose yields^{123,125,126}.

In alkaline hydrolysis, alkali induces swelling leading to increase in internal surface area. Next, a decrease in degree of polymerization, and crystallinity occurs with a

consequent separation of structural linkages between lignin and carbohydrates. Then, disruption of lignin structure takes place, followed by saponification of intermolecular ester bonds that crosslink hemicelluloses and other components. This leads to an increase of LCMs porosity with removal of such crosslinks⁴. In addition, removal of acetyl and uronic acid substitutions of hemicelluloses increase accessibility of enzyme to hemicellulose and cellulose surface in a further enzymatic posthydrolysis^{1,3}.

Main advantage of these processes is the use of low temperature and pressure. Lime as compared to NaOH and KOH has lower cost and less significant safety requirements. It can be recovered from hydrolyzate by reaction with CO₂, so that formed carbonate can then be reconverted to lime³. Unlike acid-catalyzed pretreatments, a limitation occurs because some alkali is converted to irrecoverable salts or incorporated as salts into biomass³.

Alkaline Peroxide

Addition of an oxidant agent (air/oxygen¹¹² or H₂O₂) to alkaline (lime or NaOH catalyzed) pretreatment can greatly improve performance, by favoring lignin removal. These treatments are applied in batch mode, either directly to biomass¹³⁰, or to steam exploded¹³¹⁻¹³³ or hydrothermally processed biomass¹³⁴. H₂O₂ treatment (1-3%; reaction time, 45 min to 5 h; temp., 30-80°C; optimal pH, 11.5¹³¹⁻¹³⁶) is not very efficient, presenting a lower effect as compared to NaOH treated biomass, but it gives higher delignification than acid hydrolysis, as seen for cotton stalks¹²³. Reaction mechanism is similar as for alkaline hydrolysis, but it is complemented with direct oxidative effect over lignin. H₂O₂ over air/oxygen do not require expensive high-pressure equipments except some safety issues. Alkaline peroxide treatments seem to have a faster kinetics at low temperature, thus presenting technological and economical advantages over lime and NaOH catalyzed pretreatments. Its association with steam explosion, or hydrothermal process seems to be an effective strategy to selectively recover and potentially upgrade lignocellulosic fractions.

Ammonia Fiber Explosion (AFEX)

AFEX can be presented as a combination of steam-explosion and alkaline pretreatments processes¹³⁷. Biomass is treated in batch mode with liquid anhydrous ammonia (1-2 kg ammonia/kg biomass) at moderate temperatures (40-140°C) and high pressure (250-300 psi)

for few minutes, after which pressure is rapidly released^{4,138,139}. In AFEX, reaction mechanism produces a combination of chemical and physical effects that induces cleavage of lignin-carbohydrate complex¹⁴⁰, hemicellulose hydrolysis, and cellulose decrystallization, that further lead to an increased surface area. These modifications enable near complete enzymatic conversion of cellulose and hemicelluloses to fermentable sugars at low to moderate enzyme loadings^{31,138}. Although, this process can be considered a dry to dry process as dry mass recovery following AFEX treatment is 100%¹³⁸, but water washing have greatly improved glucan conversion, due to removal of phenolic extractives from AFEX-treated biomass¹⁴⁰.

AFEX has been applied successfully to herbaceous and agricultural residues¹³⁷⁻¹⁴³ with approx. 100% of theoretical glucose yield, but it only works moderately well on hardwoods, and is not attractive for softwood derived materials^{3,31,141}. Also, it involves high costs associated to ammonia, its recovery, and considerable safety issues regarding practical use of ammonia³¹. On the other hand, economy is positively influenced by high total sugar yields achieved, without the presence of potential inhibitors (sugar degradation products³) and possibility to recover feedstock protein¹⁴⁴ as a biorefinery co-product (animal feed).

Ammonia Recycling Percolation (ARP)

In ARP, aqueous ammonia is used in flow-through mode using a column reactor containing biomass. It contains following parameters: ammonia conc., 2.5-20% (typically, 10-15%); reaction time, up to 90 min^{3,4}; solid conc., 15-30% (w/w); temp., 140-170°C (up to 210°C¹⁴⁵); and percolation rate, 5 ml/min^{1,145}. This process has already been successfully applied to hardwoods^{145,146}, corn stover¹⁴⁷⁻¹⁵⁰, and with a slight less efficiency to softwood pulp mill sludges¹⁵¹, producing highly effective delignification (60-85%)^{145,147,148} and cellulose hydrolysis yields close to the theoretical value. ARP process can also solubilize hemicellulose (40-60%, mainly in oligomeric form), but cellulose fraction remains intact (solubilization <10%)^{145-148,151}.

High enzymatic digestibility by ARP pretreated biomass can be explained by simultaneous removal of lignin and hemicellulose. Aqueous ammonia reaction mechanism is cleavage of ether and ester bonding in lignin carbohydrate complex and swelling. SEM indicated that biomass structure got deformed and its fibers exposed by ARP^{147,148}. Crystallinity index increased with

pretreatment reflecting removal of amorphous portion of biomass. Crystalline structure of cellulose in biomass, however, was not changed by ARP treatment^{147,148}. ARP is not economical process¹.

Hemicellulose Path: Combined Hydrolysis and Posthydrolysis

Most promising pretreatment option for hemicellulose breakdown is dilute acid, which significantly increases susceptibility to hydrolysis for cellulose. However, it produces fermentation inhibitors, and acid utilization is a critical and expensive issue, resulting in a waste disposal problem, and thereby requiring use of expensive corrosion-resistant equipments. Furthermore, lignin valorization potential is decreased. This may eventually shift balance in favor of a slightly less effective hydrolytic pretreatments, but also less problematic and environment friendly². In this case, autohydrolysis or steam-explosion may lead the run for best pretreatment technology for LCM biorefineries. Moreover, current research efforts may lead to get higher yields eventually similar to diluted acid yields². Although, autohydrolysis process is currently at laboratory/pilot stage, it could become commercially available, in mid-term, with process yields forecasted around 88-98%, this is higher than for dilute acid or steam-explosion.

Many of these pretreatment options render soluble hemicellulose, either totally or in a very significant quantity, in oligomeric form (for autohydrolysis, values up to 60-80% reported^{55,58,79,152-155}). Oligosaccharides do have significant market potential either as specialty pharmaceuticals, chemicals or food additives¹⁵⁶⁻¹⁵⁸. Therefore, to fully upgrade this stream, other products must be targeted, such as bioethanol, organic alcohols such as polyols⁵, namely arabitol and more relevant xylitol¹⁵⁹⁻¹⁶², organic acids, yeast extract^{163,164}, 1,2-propanediol, 2,3-butanediol, and aromatic chemical intermediates^{165,166}. Hydrolysis of hemicellulosic oligosaccharides is almost a compulsory requirement to upgrade hemicellulosic sugar stream. Actually, there are not yet many effective microbial catalysts that can directly metabolize oligosaccharides to produce marketable products, exceptions being production of xylanases by fungi (*Aspergillus niger*¹¹²) or actinomycetes¹⁶⁷. Posthydrolysis options for oligosaccharide hydrolysis can be reduced to acid^{57,63,109,161,168-171}, or enzymatic catalyzed processes^{62,161,172-175}. This process has been applied to hydrolyzates obtained from all type of materials (softwoods^{109,170}, hardwoods¹⁶⁸ and

herbaceous^{57,63,161,169,171}) catalyzed by H₂SO₄ (conc. 0.5-6.5% w/w) at 100.5-135°C and reaction time up to 10 h^{57,109,161,168,169}.

Under fully optimized conditions, sugar recovery is around 100%^{57,109,161,168,169,171}, as compared to standard dilute acid hydrolysis (121°C, 4% H₂SO₄ and 60 min). Actually, this can be considered major advantage of acid posthydrolysis procedure. Other advantages associated to this process are its high-speed and low catalyst cost. An increase in hydrolyzate fermentability due to a lower inhibitory effect has also been reported¹⁷⁰. On the other hand, it can induce significant equipment corrosion and hence higher equipment costs. Media neutralization is an absolute need, thus increasing both alkali consumption and costs associated with salts (typically gypsum) removal.

Actually, as much of hemicellulose complex structure is still present in oligosaccharides^{79,176}, action of several enzyme activities are usually required for complete hydrolysis. These enzymes act synergistically, since endoxylanase activity is highly dependent on the presence of debranching enzymes and vice versa^{62,165,174,177-179}, as well as chain length and degree of substitution¹⁸⁰. Toxic/inhibitors compounds potentially present in hydrolysates can significantly reduce enzyme activity^{62,181-183}. Indeed, each enzyme performance will largely depend on the type and concentration of inhibitors. Phenolic compounds are particularly toxic, once they easily form crosslinkage with proteins, inactivating them¹⁸⁴. Walch⁶² also reported inhibitor effect of tannins on xylanase activity. On the other hand, there are no evidences of synergism or cumulative toxic effect amongst different inhibitors simultaneously present in hydrolyzates¹⁸³.

Main advantage of enzymatic posthydrolysis over acidic process is milder operation conditions (temperature and pH), which leads to reaction media free of further sugar degradation compounds that can limit microbial performance, together with potential economical advantages related to energy savings and equipment cost. Main bottleneck is slow kinetics that may induce considerable problems for large-scale operations, besides cost of enzyme preparations.

Integration of Biomass Pretreatments in Biorefinery Concept

Numerous hydrolysis methods or combinations are available having specific advantages and disadvantages and yielding very different reaction products. Table 3

Table 3—Hemicellulosic hydrolyzates composition (g.l⁻¹) obtained from different lignocellulosic raw materials by dilute acid hydrolysis

Material	Xyl	Glc	Ara	Gal	Man	Acetic	Furfural	HMF	Phenolics
<i>Agricultural byproducts</i>									
Sugarcane bagasse ¹⁸⁵	46.0	3.0	5.0	-	-	10.0	0.60	< 0.1	-
Sugarcane bagasse ¹⁸⁶	18.5	1.2	1.7	-	-	6.5	< 0.1	< 0.1	-
Sugarcane bagasse ¹⁸⁷	26.4	5.5	2.1	-	-	5.5	< 0.5	< 0.1	-
Sugarcane bagasse ¹⁶⁴	18.5	5.1	-	-	-	3.7	2.0	< 0.1	-
Corn cobs ¹⁸⁸	35.3	3.2	4.6	-	-	3.7	0.30	< 0.1	-
Corn stover ¹⁸⁸	22.5	2.0	3.6	-	-	2.3	0.30	< 0.1	-
Barley bran ¹⁸⁸	35.6	5.9	7.1	-	-	2.4	0.30	< 0.1	-
Rice straw ¹⁸⁹	16.2	6.0	2.2	-	-	0.63	-	-	-
Rice straw ¹⁸⁹	16.4	4.4	2.4	-	-	1.4	0.41	< 0.1	-
<i>Hardwoods</i>									
Oak ¹⁹⁰	43.5	9.0	0	3.3	2.9	10.9	0.30	0.9	-
Oak+yellow poplar ¹⁹¹	44.8	2.4	-	-	-	9.2	0.91	0	-
Eucalyptus ¹⁹²	30.0	1.5	2.8	3.7	1.0	10	-	-	-
Eucalyptus ¹⁹³	17.0	2.8	1.9	-	-	2.3	0.50	-	-
Eucalyptus ¹²⁷	18.0	3.6	0.6	-	-	5.2	< 0.5	-	-
Eucalyptus ¹⁹⁴	19.2	2.5	0.4	-	-	5.0	-	-	-
Eucalyptus ¹⁸⁸	17.1	1.7	2.1	-	-	5.2	0.50	< 0.1	-
Aspen ¹⁹⁵	12.3	0.9	-	-	-	3.1	0.14	-	0.63 ^a
Aspen ¹⁹⁵	23.7	1.7	-	-	-	6.1	0.28	-	1.28 ^a
Aspen ¹⁹⁶	15.3	6.3	0.9	0.8	1.2	0.6	-	-	-
Birch ¹⁹⁷	15.4	24.5	-	-	2.5	8.3	2.2	7.3	-
<i>Softwoods</i>									
Spruce ¹⁹⁷	3.3	39.0	-	-	12.3	3.2	2.2	7.3	-
Spruce ^{b, 198}	7.8	20.0	-	4.2	18.1	3.0	0.8	2.0	2.4
Douglas fir ¹⁹⁹	15.6	42.0	4.8	10.3	32.6	7.3	2.0	4.1	-

Xyl, xylose; Glc, glucose; Ara, arabinose; Gal, galactose; Man, mannose; HMF, hydroxymethylfurfural, ^a*p*-hydroxybenzoic acid and vanillin; ^bmajority

Table 4—Relevant enzymatic activities for the enzymatic posthydrolysis of xylooligosaccharides²⁰⁰

Enzyme	EC	Hydrolyzed linkage	Substrate	Main product
Endoxylanase	3.2.1.8	Internal β-1,4	Main chain	Oligomers
Exoxylanase	n.c.	Terminal β-1,4 (reducing end)	Main chain	Xylose, xylobiose
β-Xylosidase	3.2.1.37	Terminal β-1,4 (non-reducing end)	Oligomers	Xylose
Arabinosidase	3.2.1.55		Side groups	Arabinose
Glucuronidase	3.2.1.139		Side groups	Methylglucuronic acids
Acetyl xylan esterase	3.1.1.72	Ester bond	Side groups	Acetic acid
Feruloyl esterase	3.1.1.73	Ester bond	Side groups	Ferulic acid
n.c., Not yet classified				

shows different hemicellulosic hydrolyzates composition^{127,164,185-199} after dilute acid hydrolysis of LCM. Table 4 presents most important enzyme activities²⁰⁰ required for hydrolysis of xylooligosaccharides obtained from hardwoods and

herbaceous type materials. Fig. 2 presents a cartoon of typical polymeric composition after BP as a function of reaction pH characteristic of each pretreatment. Generally, low pH pretreatments tend to solubilize hemicellulose and render it in oligomeric form, conversely

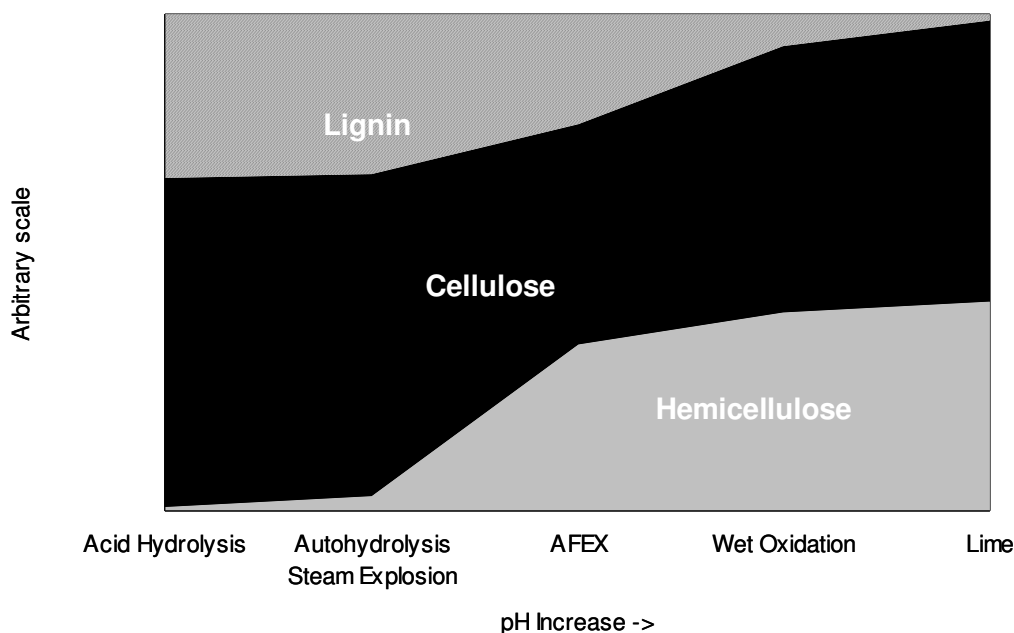


Fig. 2—Typical polymeric solids composition after biomass pretreatment as a function of reaction pH characteristic of each pretreatment

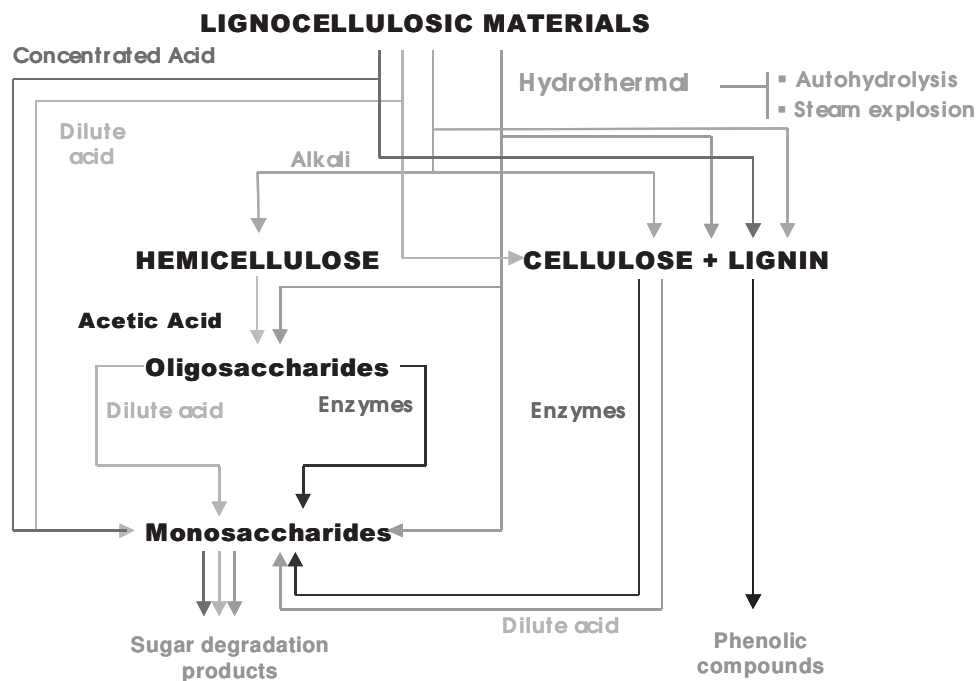


Fig. 3—Main hydrolysis processes options for biomass fractionation in a biorefinery context

to alkaline pretreatments that selectively solubilize lignin. In depth knowledge of main reactions and consequences of each pretreatment can help to better design most convenient strategy to treat a given material for a specific aim. Fig. 3 presents a simple schematic representation of most commonly used processes and their main effects on LCM.

Choice for BP technologies heavily influences cost and performance in subsequent hydrolysis and fermentation. Therefore, following criteria should be met: i) Maximize pentoses yield in non-degraded form; ii) Produce reactive (cellulosic) fibers; iii) Get hydrolysates with no significant inhibition of fermentation; iv) No extensive feedstock size reduction; v) Design reactors

of high solids loading and built from materials not expensive ones; and vi) Produce zero waste^{1,2}.

References

- Huber G W, Iborra S & Corma A, Synthesis of transportation fuels from biomass: Chemistry, catalysts, and engineering, *Chem Rev*, **106** (2006) 4044-4098.
- Hamelinck C N, van Hooijdonk G & Faaij A P C, Ethanol from lignocellulosic biomass: techno-economic performance in short-, middle- and long-term, *Biomass Bioenergy*, **28** (2005) 384-410.
- Mosier N, Wyman C, Dale B, Elander R, Lee Y Y, Holtzapple M & Ladisch M, Features of promising technologies for pretreatment of lignocellulosic biomass, *Biores Technol*, **96** (2005) 673-686.
- Sun Y & Cheng J, Hydrolysis of lignocellulosic materials for ethanol production: a review, *Biores Technol*, **83** (2002) 1-11.
- Werpy T, Petersen G, Aden A, Bozell J, Holladay J, White J, Manheim A, Elliot D, Lasure L, Jones S, Gerber M, Ibsen K, Lumberg L & Kelley S, *Top Value Added Chemicals from Biomass. Volume I - Results of Screening for Potential Candidates from Sugars and Synthesis Gas* [U S Department of Energy (DOE), Oak Ridge, TN] 2004.
- Kamm B, Kamm M, Gruber P R & Kromus S, Biorefinery systems - An overview, in *Biorefineries - Industrial Processes and Products. Status Quo and Future Directions*, edited by B Kamm, P R Gruber & M Kamm (Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim) 2006, 3-40.
- Wright L, Boundy B, Perlack B, Davis S & Saulsbury B, *Biomass Energy Data Book* [U S Department of Energy (DOE), Oak Ridge, TN] 2006.
- Kamm B & Kamm M, Principles of biorefineries, *Appl Microbiol Biotechnol*, **64** (2004) 137-145.
- Ohara H, Biorefinery, *Appl Microbiol Biotechnol*, **62** (2003) 474-477.
- Arato C, Biorefining: Back to the future, *Innovation, Spr* (2002) 12-15.
- Duarte L C, Esteves M P, Carvalho F, Vicente P & Gírio F M, Os subprodutos agro-industriais de natureza lenhocelulósica: caracterização da situação portuguesa, *Engenharia Química*, **5** (2007) 56-62.
- Greer D, Creating cellulosic ethanol: Spinning straw into fuel, *Biocycle*, **46** (2005) 61.
- Finlay M, Old efforts at new uses: A brief history of chemurgy and the American search for biobased materials, *J Ind Ecol*, **7** (2003) 33-46.
- Realff M J & Abbas C, Industrial symbiosis - refining the biorefinery, *J Ind Ecol*, **7** (2004) 5-9.
- Wooley R, Ruth M, Sheehan J & Ibsen K, *Lignocellulosic biomass to ethanol process design and economics utilizing co-current dilute acid prehydrolysis and enzymatic hydrolysis current and futuristic scenarios*, **NREL/TP-580-26157** (Golden, CO, NREL - National Renewable Energy Laboratory) 1999.
- Kamm B & Kamm M, Biorefinery - Systems, *Chem Biochem Engg Qrtly*, **18** (2004) 1-6.
- McAloon A, Taylor F, Yee W, Ibsen K & Wooley R, *Determining the cost of producing ethanol from corn starch and lignocellulosic feedstocks*, **NREL/TP-580-28893** (Golden, CO, NREL - National Renewable Energy Laboratory) 2000.
- Alzate C A C & Toro O J S, Energy consumption analysis of integrated flowsheets for production of fuel ethanol from lignocellulosic biomass, *Energy*, **31** (2006) 2447-2459.
- Greer D, Realities, opportunities for cellulosic ethanol, *Biocycle*, **48** (2007) 46.
- Arato C, Pye E K & Gjennestad G, The lignol approach to biorefining of woody biomass to produce ethanol and chemicals, *Appl Biochem Biotechnol*, **121** (2005) 871-882.
- Duarte L C, Esteves M P, Carvalho F & Gírio F M, Biotechnological Valorization Potential Indicator for lignocellulosic materials, *Biotechnol J*, **2** (2007) 1556-1563.
- Kaylen M, Van Dyne D L, Choi Y S & Blase N, Economic feasibility of producing ethanol from lignocellulosic feedstocks, *Biores Technol*, **72** (2000) 19-32.
- Wyman C E, Twenty years of trials, tribulations, and research progress in bioethanol technology: selected key events along the way, *Appl Biochem Biotechnol*, **91-93** (2001) 5-21.
- Dien B S, Cotta M A & Jeffries T W, Bacteria engineered for fuel ethanol production: current status, *Appl Microbiol Biotechnol*, **63** (2003) 258-266.
- Buckley M R & Wall J, *Microbial Energy Conversion* (American Academy of Microbiology, Washington, DC) 2006.
- Breaking the biological barriers to cellulosic ethanol: A joint research agenda* (U S Department of Energy. Office of Science and Office of Energy Efficiency and Renewable Energy) 2006.
- Lynd L R, Laser M S, Bransby D, Dale B E, Davison B, Hamilton R, Himmel M, Keller M, McMillan J D, Sheehan J & Wyman C E, How biotech can transform biofuels, *Nat Biotech*, **26** (2008) 169-172.
- Larsson S, Palmqvist E, Hahn-Hägerdal B, Tengborg C, Stenberg K, Zacchi G & Nilvebrant N O, The generation of fermentation inhibitors during dilute acid hydrolysis of softwood, *Enzyme Microbiol Technol*, **24** (1999) 151-159.
- Galbe M & Zacchi G, A review of the production of ethanol from softwood, *Appl Microbiol Biotechnol*, **59** (2002) 618-628.
- Fengel D & Wegener G, *Wood. Chemistry, Ultrastructure, Reactions* (Walter de Gruyter, Berlin, New York) 1984.
- Ogier J C, Ballerini D, Leygue J P, Rigal L & Pourquie J, *Ethanol Production from Lignocellulosic Biomass*, **vol 54** (Oil & Gas Science and Technology-Revue de l' Institut Francais du Petrole) (1999) 67-94.
- Camacho F, González-Tello P, Jurado E & Robles A, Microcrystalline-cellulose hydrolysis with concentrated sulphuric acid, *J Chem Technol Biotechnol*, **67** (1996) 350-356.
- Bhandari N, McDonald D G & Bakhshi N N, Kinetic studies of corn stover saccharification using sulfuric acid, *Biotechnol Bioengg*, **26** (1984) 320-327.
- Ranganathan S, McDonald D G & Bakhshi N N, Kinetic studies of wheat straw hydrolysis using sulfuric acid, *Can J Chem Engg*, **63** (1985) 840-844.
- Goldstein I S, Acid processes for cellulose hydrolysis and their mechanisms, in *Wood and Agricultural Residues* (Academic Press Inc., New York) 1983, 315-328.
- Parisi F, Advances in lignocellulosics hydrolysis and the utilization of the hydrolysates, *Adv Biochem Eng Biotechnol*, **38** (1989) 53-87.

- 37 Zhang Y H P, Ding S Y, Mielenz J R, Cui J B, Elander R, Laser M, Himmel M E, McMillan J R & Lynd L R, Fractionating recalcitrant lignocellulose at modest reaction conditions, *Biotechnol Bioeng*, **97** (2007) 214-223.
- 38 Hawley M C, Downey K W & Lamport D T, in *Cellulose - Structure, Modification and Hydrolysis*, edited by R A Young & R M Rowell (John Wiley, New York) 1986, 297.
- 39 McWilliams R C & van Walsum G P, Comparison of aspen wood hydrolysates produced by pretreatment with liquid hot water and carbonic acid, *Appl Biochem Biotechnol*, **98-100** (2002) 109-121.
- 40 van Walsum G P, Severity function describing the hydrolysis of xylan using carbonic acid, *Appl Biochem Biotechnol*, **91-93** (2001) 317-329.
- 41 van Walsum G P & Shi H, Carbonic acid enhancement of hydrolysis in aqueous pretreatment of corn stover, *Biores Technol*, **93** (2004) 217-226.
- 42 Cahela D R, Lee Y Y & Chambers R P, Modeling of percolation process in hemicellulose hydrolysis, *Biotechnol Bioeng*, **25** (1983) 3-17.
- 43 Kim B J, Lee Y Y & Torget R, An optimal temperature policy of percolation process as applied to dilute-acid hydrolysis of biphasic hemicellulose, *Appl Biochem Biotechnol*, **39** (1993) 119-129.
- 44 Kim B J, Lee Y Y & Torget R, Modified percolation process in dilute-acid hydrolysis of biphasic hemicellulose, *Appl Biochem Biotechnol*, **45-46** (1994) 113-129.
- 45 Torget R W, Hayward T K & Elander R, Total hydrolysis of lignocellulosic biomass using very dilute acid employing a novel shrinking bed reactor configuration, in *19th Symp on Biotechnol for Fuels and Chemicals* (Colorado Springs, EUA) 1997, Presentation 4.
- 46 Lee Y Y, Iyer P & Torget R W, *Dilute-Acid Hydrolysis of Lignocellulosic Biomass*, edited by G T Tsao (Springer-Verlag, Berlin) 1999, 93-115.
- 47 Mosier N S, Sarikaya A, Ladisch C M & Ladisch M R, Characterization of dicarboxylic acids for cellulose hydrolysis, *Biotechnol Progr*, **17** (2001) 474-480.
- 48 Mosier N S, Ladisch C M & Ladisch M R, Characterization of acid catalytic domains for cellulose hydrolysis and glucose degradation, *Biotechnol Bioeng*, **79** (2002) 610-618.
- 49 Bobleter O & Pape G, Method to degrade wood, bark and other plant materials, *Aust Pat 263661*, 1968.
- 50 Lora J H & Wayman M, Delignification of hardwoods by autohydrolysis and extraction, *Tappi*, **61** (1978) 47-50.
- 51 Carrasco F, Fundamentos del fraccionamiento de la biomasa, *Afinidad*, **46** (1989) 425-429.
- 52 Schultz T P & McGinnis G D B C J, Similarities and differences in pretreating woody biomass by steam explosion, wet oxidation, autohydrolysis, and rapid steam hydrolysis/continuous extraction, in *Energy from Biomass and Wastes VIII* (Lake Buena Vista, Florida, EUA) 1984.
- 53 Rubio M, Tortosa J F, Quesada J & Gómez D, Fractionation of lignocellulosics. Solubilization of corn stalk hemicelluloses by autohydrolysis in aqueous media, *Biomass Bioenergy*, **15** (1998) 483-491.
- 54 Tortosa J F, Rubio M & Soler A, Autohidrólisis de tallo de maíz en suspensión acuosa, *Afinidad*, **52** (1995) 305-311.
- 55 Garrote G, Domínguez H & Parajó J C, Mild autohydrolysis: an environmentally friendly technology for xylooligosaccharide production from wood, *J Chem Technol Biotechnol*, **74** (1999) 1101-1109.
- 56 Heitz M, Carrasco F, Rubio M, Chauvette G, Chornet E, Jaulin L & Overend R P, Generalized correlations for the aqueous liquefaction of lignocellulosics, *Can J Chem Eng*, **64** (1986) 647-650.
- 57 Saska M & Ozer E, Aqueous extraction of sugarcane bagasse hemicellulose and production of xylose syrup, *Biotechnol Bioeng*, **45** (1995) 517-523.
- 58 Allen S G, Schulman D, Lichwa J, Antal M J, Laser M & Lynd L R, A comparison between hot liquid water and steam fractionation of corn fiber, *Ind Eng Chem Res*, **40** (2001) 2934-2941.
- 59 Overend R P & Chornet E, Fractionation of lignocellulosics by steam-aqueous pretreatments, *Phil Trans R Soc Lond*, **A321** (1987) 523-536.
- 60 Bonn G, Concin R & Bobleter O, Hydrothermolysis: a new process for the utilization of biomass, *Wood Sci Technol*, **17** (1983) 195-202.
- 61 Hörmeyer H F, Schwald W, Bonn G & Bobleter O, Hydrothermolysis of birch wood as pretreatment for enzymatic saccharification, *Holzforschung*, **42** (1988) 95-98.
- 62 Walch E, Zemmann A J, Schinner F, Bonn G & Bobleter O, Enzymatic saccharification of hemicellulose obtained from hydrothermally pretreated sugar-cane bagasse and beech bark, *Biores Technol*, **39** (1992) 173-177.
- 63 Allen S G, Kam L C, Zemmann A J & Antal M J, Fractionation of sugar cane with hot, compressed, liquid water, *Ind Eng Chem Res*, **35** (1996) 2709-2715.
- 64 Bobleter O, Vidotti R, Zemmann A & Prutsch W, Hydrothermal pretreatment of bagasse and wheat straw, in *Proc fifth E C Conf on Biomass for Energy and Industry*, edited by G Grassi, G Gosse & G dos Santos (Elsevier Applied Science, London, Lisboa) 1989, 31-35.
- 65 Conner A H, Kinetic modeling of hardwood prehydrolysis. Part I. Xylan removal by water prehydrolysis, *Wood Fiber Sci*, **16** (1984) 268-277.
- 66 Weil J, Sarikaya A, Rau S L, Goetz J, Ladisch C M, Brewer M, Hendrickson R & Ladisch M R, Pretreatment of yellow poplar sawdust by pressure cooking in water, *Appl Biochem Biotechnol*, **68** (1997) 21-40.
- 67 Garrote G, Domínguez H & Parajó J C, Hydrothermal processing of lignocellulosic materials, *Holz Als Roh-und Werkstoff*, **57** (1999) 191-202.
- 68 Abatzoglou N, Chornet E, Belkacemi K & Overend R P, Phenomenological kinetics of complex-systems - the development of a generalized severity parameter and its application to lignocellulosics fractionation, *Chem Eng Sci*, **47** (1992) 1109-1122.
- 69 Torres M R, Heitz M, Chauvette G, Chornet E & Overend R P, Conversion and solubilization profiles of a prototype hardwood (*Populus tremuloides*) following aqueous thermomechanical pre-treatment, *Biomass*, **10** (1986) 85-96.
- 70 Bouchard J, Nguyen T S, Chornet E & Overend R P, Analytical methodology for biomass pretreatment. Part I: Solid residues, *Biomass*, **23** (1990) 243-261.
- 71 Brownell H H & Saddler J N, Steam-explosion pretreatment for enzymatic hydrolysis, *Biotechnol Bioeng Symp*, **14** (1984) 55-68.

- 72 Martínez J M, Reguant J, Montero M A, Montané D, Salvadó J & Farriol X, Hydrolytic pretreatment of softwood and almond shells. Degree of polymerization and enzymatic digestibility of the cellulose fraction, *Ind Eng Chem Res*, **36** (1997) 688-696.
- 73 van Walsum G P, Allen S G, Spencer M J, Laser M S, Antal M J & Lynd L R, Conversion of lignocellulosics pretreated with liquid hot water to ethanol, *Appl Biochem Biotechnol*, **57-58** (1996) 157-170.
- 74 Kim S B & Lee Y Y, Kinetics in acid-catalyzed hydrolysis of hardwood hemicellulose, *Biotechnol Bioeng Symp*, **17** (1987) 71-84.
- 75 Aoyama M, Seki K & Saito N, Solubilization of bamboo grass xylan by steaming treatment, *Holzforschung*, **49** (1995) 193-196.
- 76 Springer E L, Prehydrolysis of hardwoods with dilute sulfuric acid, *Ind Eng Chem Prod Res Develop*, **24** (1985) 614-623.
- 77 Brownell H H, Yu E K C & Saddler J N, Steam-explosion pretreatment of wood: effect of chip size, acid, moisture content and pressure drop, *Biotechnol Bioeng*, **28** (1986) 792-801.
- 78 Ballesteros I, Oliva J M, Navarro A A, Gonzalez A, Carrasco J & Ballesteros M, Effect of chip size on steam explosion pretreatment of softwood, *Appl Biochem Biotechnol*, **84-86** (2000) 97-110.
- 79 Carvalho F, Esteves M P, Parajó J C, Pereira H & Gírio F M, Production of oligosaccharides by autohydrolysis of brewery's spent grain, *Biores Technol*, **91** (2004) 93-100.
- 80 Carrasco F, Chornet E, Overend R P & Heitz M, Fractionnement de deux bois tropicaux (Eucalyptus et Wapa) par traitement thermomécanique en phase aqueuse. Partie II: Caractéristiques chimiques des résidus et considérations cinétiques sur la solubilisation des hémicelluloses, *Can J Chem Eng*, **65** (1987) 71-77.
- 81 Conner A H, Kinetic modeling of hardwood prehydrolysis. Part I. Xylan removal by water prehydrolysis, *Wood Fiber Sci*, **16** (1984) 268-277.
- 82 Wayman M, Fundamental principals and practical consequences in the bioconversion of biomass to ethanol, in *Intl Symp on Ethanol from Biomass* (Royal Soc Can Proc,) 1982, 628-644.
- 83 Wayman M, Alcohol from cellulose: The autohydrolysis-extraction process, in *NTIS document no conf. B010302* (US Dep of Commerce, Springfield, Va) 1980.
- 84 Mok W S L & Antal M J, Uncatalyzed solvolysis of whole biomass hemicellulose by hot compressed liquid water, *Ind Eng Chem Res*, **31** (1992) 1157-1161.
- 85 Lamptey J, Robinson C W & Moo-Young M, Enhanced enzymatic hydrolysis of lignocellulosic biomass pretreated by low-pressure steam autohydrolysis, *Biotechnol Lett*, **7** (1985) 531-536.
- 86 Kubikova J, Zemmann A, Krkoska P & Bobleter O, Hydrothermal pretreatment of wheat straw for the production of pulp and paper, *Tappi J*, **79** (1996) 163-169.
- 87 Dunlop A P, Furfural formation and behavior, *Ind Eng Chem*, **40** (1948) 204-209.
- 88 Ulbricht R J, Northup S J & Thomas J A, A review of 5-hydroxymethylfurfural (HMF) in parenteral solutions, *Fundamental Appl Toxicol*, **4** (1984) 843-853.
- 89 Mason W H, Apparatus and process of explosion defibration of lignocellulosic material, *US Pat 1655618*, 1929.
- 90 Foody P, Method for obtaining superior yields of accessible cellulose and hemicellulose from lignocellulosic materials, *Can Pat CA 1163058*, 1984.
- 91 DeLong E A, Method of rendering lignin separable from cellulose and hemicellulose and the product so produced, *Pat Can CA 1141376*, 1983.
- 92 Brownell H H & Saddler J N, Steam pretreatment of lignocellulosic material for enhanced enzymatic hydrolysis, *Biotechnol Bioeng*, **29** (1987) 228-235.
- 93 Heitz M, Capek-Menard E, Koeberle P G, Gagné J, Chornet E, Overend R P, Taylor J D & Yu E, Fractionation of *Populus tremuloides* at the pilot-plant scale - optimization of steam pretreatment conditions using the stake-II technology, *Biores Technol*, **35** (1991) 23-32.
- 94 Chornet E & Overend R P, Phenomenological kinetics and reaction engineering aspects of steam/aqueous treatments, in *Proc Int Workshop on Steam Explosion Techniques: Fundamentals and Industrial Applications* 1988, 21-58.
- 95 Schultz T P, Templeton M C, Biermann C J & McGinnis G D, Steam explosion of mixed hardwood chips, rice hulls, corn stalks, and sugar cane bagasse, *J Agri Food Chem*, **32** (1984) 1166-1172.
- 96 Martínez J, Negro M J, Sáez F, Manero J, Sáez R & Martín C, Effect of acid steam explosion on enzymatic hydrolysis of *O. nervosum* and *C. cardunculus*, *Appl Biochem Biotechnol*, **24-5** (1990) 127-134.
- 97 Ballesteros I, Oliva J M, Negro M J, Manzanares P & Ballesteros M, Enzymic hydrolysis of steam exploded herbaceous agricultural waste (*Brassica carinata*) at different particule sizes, *Process Biochem*, **38** (2002) 187-192.
- 98 Cara C, Romero I, Oliva J M, Saez F & Castro E, Liquid hot water pretreatment of olive tree pruning residues, *Appl Biochem Biotechnol*, **137** (2007) 379-394.
- 99 Ruiz E, Cara C, Manzanares P, Ballesteros M & Castro E, Evaluation of steam explosion pre-treatment for enzymatic hydrolysis of sunflower stalks, *Enzyme Microbiol Technol*, **42** (2008) 160-166.
- 100 Mason W H, Apparatus and process of explosion defibration of lignocellulosic material, *Pat Am US 1655618*, 1929.
- 101 Mamers H, Yuritta J P & Menz D J, Explosion pulping of bagasse and wheat straw, *Tappi*, **64** (1981) 93-96.
- 102 DeLong E A, Method of rendering lignin separable from cellulose and hemicellulose in lignocellulosic material and the product so produced. *Pat Can CA 1096374*, 1981.
- 103 Mackie K L, Brownell H H, West K L & Saddler J N, Effect of sulfur dioxide and sulfuric acid on steam explosion of aspenwood, *J Wood Chem Technol*, **5** (1985) 405-425.
- 104 Nguyen Q A, Tucker M P, Boynton B L, Keller F A & Schell D J, Dilute acid pretreatment of softwoods - Scientific note, *Appl Biochem Biotechnol*, **70-72** (1998) 77-87.
- 105 Tengborg C, Stenberg K, Galbe M, Zacchi G, Larsson S, Palmqvist E & Hahn-Hägerdal B, Comparison of SO₂ and H₂SO₄ impregnation of softwood prior to steam pretreatment on ethanol production, *Appl Biochem Biotechnol*, **70-72** (1998) 3-15.
- 106 Martín C, Galbe M, Nilvebrant N O & Jönsson L J, Comparison of the fermentability of enzymatic hydrolyzates of sugarcane bagasse pretreated by steam explosion using

- different impregnating agents, *Appl Biochem Biotechnol*, **98-100** (2002) 699-716.
- 107 Eklund R, Galbe M & Zacchi G, The influence of SO₂ and H₂SO₄ impregnation of willow prior to steam pretreatment, *Biores Technol*, **52** (1995) 225-229.
 - 108 Boussaid A, Robinson J, Cai Y J, Gregg D J & Saddler J R, Fermentability of the hemicellulose-derived sugars from steam-exploded softwood (Douglas fir), *Biotechnol Bioeng*, **64** (1999) 284-289.
 - 109 Shevchenko S M, Chang K, Robinson J & Saddler J N, Optimization of monosaccharide recovery by post-hydrolysis of the water-soluble hemicellulose component after steam explosion of softwood chips, *Biores Technol*, **72** (2000) 207-211.
 - 110 Ramos L P, Breuil C, Kushner D J & Saddler J N, Steam pretreatment conditions for effective enzymatic hydrolysis and recovery yields of *Eucalyptus viminalis* wood chips, *Holzforschung*, **46** (1992) 149-154.
 - 111 McGinnis G D, Wilson W W & Mullen C E, Biomass pretreatment with water and high-pressure oxygen - the wet oxidation process, *Ind Eng Chem Prod Res Develop*, **22** (1983) 352-357.
 - 112 Bjerre A B, Olesen A B, Fernqvist T, Ploger A & Schmidt A S, Pretreatment of wheat straw using combined wet oxidation and alkaline hydrolysis resulting in convertible cellulose and hemicellulose, *Biotechnol Bioeng*, **49** (1996) 568-577.
 - 113 Klinke H B, Ahring B K, Schmidt A S & Thomsen A B, Characterization of degradation products from alkaline wet oxidation of wheat straw, *Biores Technol*, **82** (2002) 15-26.
 - 114 Klinke H B, Thomsen A B & Ahring B K, Potential inhibitors from wet oxidation of wheat straw and their effect on growth and ethanol production by *Thermoanaerobacter mathranii*, *Appl Microbiol Biotechnol*, **57** (2001) 631-638.
 - 115 Kin Z, The acetolysis of beech wood, *Tappi Journal*, **73** (1990) 237-238.
 - 116 Vázquez D, Lage M A, Parajó J C & Vázquez G, Fractionation of *Eucalyptus* wood in acetic acid media, *Biores Technol*, **40** (1992) 131-136.
 - 117 Pan X J, Arato C, Gilkes N, Gregg D, Mabey W, Pye K, Xiao Z Z, Zhang X & Saddler J, Biorefining of softwoods using ethanol organosolv pulping: Preliminary evaluation of process streams for manufacture of fuel-grade ethanol and co-products, *Biotechnol Bioeng*, **90** (2005) 473-481.
 - 118 Wyman C E, Dale B E, Elander R T, Holtzapple M, Ladisch M R & Lee Y Y, Comparative sugar recovery data from laboratory scale application of leading pretreatment technologies to corn stover, *Biores Technol*, **96** (2005) 2026-2032.
 - 119 Wyman C E, Dale B E, Elander R T, Holtzapple M, Ladisch M R & Lee Y Y, Coordinated development of leading biomass pretreatment technologies, *Biores Technol*, **96** (2005) 1959-1966.
 - 120 Mussatto S I, Dragone G, Rocha G J M & Roberto I C, Optimum operating conditions for brewer's spent grain soda pulping, *Carbohydr Polym*, **64** (2006) 22-28.
 - 121 Mussatto S I, Dragone G & Roberto I C, Ferulic and p-coumaric acids extraction by alkaline hydrolysis of brewer's spent grain, *Ind Crops Products*, **25** (2007) 231-237.
 - 122 Parajó J C, Alonso J L & Santos V, Development of a generalized phenomenological model describing the kinetics of the enzymatic hydrolysis of NaOH-treated pine wood, *Appl Biochem Biotechnol*, **56** (1996) 289-299.
 - 123 Silverstein R A, Chen Y, Sharma-Shivappa R R, Boyette M D & Osborne J, A comparison of chemical pretreatment methods for improving saccharification of cotton stalks, *Biores Technol*, **98** (2007) 3000-3011.
 - 124 Holtzapple M T, Davison R R, Ross M K, Aldrett-Lee S, Nagwani M, Lee C M, Lee C, Adelson S, Kaar W, Gaskin D, Shirage H, Chang N S, Chang V S & Loescher M E, Biomass conversion to mixed alcohol fuels using the MixAlco process, *Appl Biochem Biotechnol*, **77-9** (1999) 609-631.
 - 125 Vázquez D, Lage M A, Parajó J C & Alonso J L, Empirical assessment on the cellulase digestibility of processed *Eucalyptus* wood, *Appl Biochem Biotechnol*, **37** (1992) 123-139.
 - 126 Moldes A B, Cruz J M, Domínguez J M & Parajó J C, Production of a cellulosic substrate susceptible to enzymatic hydrolysis from prehydrolyzed barley husks, *Agric Food Sci Finland*, **11** (2002) 51-58.
 - 127 Parajó J C, Domínguez H & Domínguez J M, Xylitol from wood: study of some operational strategies, *Food Chem*, (1996) 531-5355.
 - 128 Sun R C & Tomkinson J, Characterization of hemicelluloses obtained by classical and ultrasonically assisted extractions from wheat straw, *Carbohydr Polym*, **50** (2002) 263-271.
 - 129 Mussatto S I, Fernandes M & Roberto I C, Lignin recovery from brewer's spent grain black liquor, *Carbohydr Polym*, **70** (2007) 218-223.
 - 130 Mishima D, Tateda M, Ike M & Fujita M, Comparative study on chemical pretreatments to accelerate enzymatic hydrolysis of aquatic macrophyte biomass used in water purification processes, *Biores Technol*, **97** (2006) 2166-2172.
 - 131 Yang B, Boussaid A, Mansfield S D, Gregg D J & Saddler J N, Fast and efficient alkaline peroxide treatment to enhance the enzymatic digestibility of steam-exploded softwood substrates, *Biotechnol Bioeng*, **77** (2002) 678-684.
 - 132 Sun X F, Xu F, Sun R C, Geng Z C, Fowler P & Baird M S, Characteristics of degraded hemicellulosic polymers obtained from steam exploded wheat straw, *Carbohydr Polym*, **60** (2005) 15-26.
 - 133 Cara C, Ruiz E, Ballesteros I, Negro M J & Castro E, Enhanced enzymatic hydrolysis of olive tree wood by steam explosion and alkaline peroxide delignification, *Process Biochem*, **41** (2006) 423-429.
 - 134 Yañez R, Alonso J L & Parajó J C, Enzymatic saccharification of hydrogen peroxide-treated solids from hydrothermal processing of rice husks, *Process Biochem*, **41** (2006) 1244-1252.
 - 135 Sun R, Tomkinson J, Geng Z C & Wang N J, Comparative studies of hemicelluloses solubilized during the treatments of maize stems with peroxy monosulfuric acid, peroxyformic acid, peracetic acid, and hydrogen peroxide Part 2. Spectroscopic and thermal characterizations, *Holzforschung*, **54** (2000) 492-496.
 - 136 Gould J M & Freer S N, High-efficiency ethanol production from lignocellulosic residues pretreated with alkaline H₂O₂, *Biotechnol Bioeng*, **26** (1984) 628-631.

- 137 Holtzaple M T, Jun J H, Ashok G, Patibandla S L & Dale B E, The Ammonia Freeze Explosion (AFEX) Process - A practical lignocellulose pretreatment, *Appl Biochem Biotechnol*, **28-9** (1991) 59-74.
- 138 Teymouri F, Laureano-Perez L, Alizadeh H & Dale B E, Optimization of the ammonia fiber explosion (AFEX) treatment parameters for enzymatic hydrolysis of corn stover, *Biores Technol*, **96** (2005) 2014-2018.
- 139 Balan V, Sousa L D, Chundawat S P S, Vismeh R, Jones A D & Dale B E, Mushroom spent straw: a potential substrate for an ethanol-based biorefinery, *J Ind Microbiol & Biotechnol*, **35** (2008) 293-301.
- 140 Chundawat S P S, Venkatesh B & Dale B E, Effect of particle size based separation of milled corn stover on AFEX pretreatment and enzymatic digestibility, *Biotechnol Bioeng*, **96** (2007) 219-231.
- 141 Holtzaple M T, Lundeen J E, Sturgis R, Lewis J E & Dale B E, Pretreatment of lignocellulosic municipal solid-waste by Ammonia Fiber Explosion (AFEX), *Appl Biochem Biotechnol*, **34-5** (1992) 5-21.
- 142 Moniruzzaman M, Dien B S, Skory C D, Chen Z D, Hespell R B, Ho N W Y, Dale B E & Bothast R J, Fermentation of corn fibre sugars by an engineered xylose utilizing *Saccharomyces* yeast strain, *World J Microbiol Biotechnol*, **13** (1997) 341-346.
- 143 Belkacemi K, Turcotte G, de Halleux D & Savoie P, Ethanol production from AFEX-treated forages and agricultural residues, *Appl Biochem Biotechnol*, **70-2** (1998) 441-462.
- 144 Bals B, Teachworth L, Dale B & Balan V, Extraction of proteins from switchgrass using aqueous ammonia within an integrated biorefinery, *Appl Biochem Biotechnol*, **143** (2007) 187-198.
- 145 Kim J S, Kim H, Lee J S, Lee J P & Park S C, Pretreatment characteristics of waste oak wood by ammonia percolation, *Appl Biochem Biotechnol*, **148** (2008) 15-22.
- 146 Yoon H H, Wu Z W & Lee Y Y, Ammonia recycled percolation process for pretreatment of biomass feedstock, *Appl Biochem Biotechnol*, **51-2** (1995) 5-19.
- 147 Kim T H & Lee Y Y, Pretreatment and fractionation of corn stover by ammonia recycle percolation process, *Biores Technol*, **96** (2005) 2007-2013.
- 148 Kim T H, Kim J S, Sunwoo C & Lee Y Y, Pretreatment of corn stover by aqueous ammonia, *Biores Technol*, **90** (2003) 39-47.
- 149 Kim T H, Lee Y Y, Sunwoo C & Kim J S, Pretreatment of corn stover by low-liquid ammonia recycle percolation process, *Appl Biochem Biotechnol*, **133** (2006) 41-57.
- 150 Zhu Y, Kim T H, Lee Y Y, Chen R & Elander R T, Enzymatic production of xylooligosaccharides from corn stover and corn cobs treated with aqueous ammonia, *Appl Biochem Biotechnol*, **129-132** (2006) 586-598.
- 151 Kim J S, Lee Y Y & Park S C, Pretreatment of wastepaper and pulp mill sludge by aqueous ammonia and hydrogen peroxide, *Appl Biochem Biotechnol*, **84-6** (2000) 129-139.
- 152 Conner A H & Lorenz L F, Kinetic modeling of hardwood prehydrolysis. Part III. Water and dilute acetic-acid prehydrolysis of southern red oak, *Wood Fiber Sci*, **18** (1986) 248-263.
- 153 Garrote G, Domínguez H & Parajó J C, Kinetic modelling of corncob autohydrolysis, *Process Biochem*, **36** (2001) 571-578.
- 154 Garrote G, Domínguez H & Parajó J C, Fractionation of corncobs in aqueous media, *Afinidad*, **59** (2002) 357-363.
- 155 Garrote G, Domínguez H & Parajó J C, Interpretation of deacetylation and hemicellulose hydrolysis during hydrothermal treatments on the basis of the severity factor, *Process Biochem*, **37** (2002) 1067-1073.
- 156 Tuohy K M, Kolida S & Gibson G R, Use of probiotics and prebiotics for improving gut health, *Agro Food Ind Hi-Tech*, **15** (2004) 33-35.
- 157 Nabarlantz D, Montané D, Kardosova A, Bekesova S, Hribalova V & Ebringerova A, Almond shell xylo-oligosaccharides exhibiting immunostimulatory activity, *Carbohydr Res*, **342** (2007) 1122-1128.
- 158 Moure A, Gullón P, Domínguez H & Parajó J C, Advances in the manufacture, purification and applications of xylo-oligosaccharides as food additives and nutraceuticals, *Process Biochem*, **41** (2006) 1913-1923.
- 159 da Silva D D V, de Mancilha I M, da Silva S S & Felipe M D D, Improvement of biotechnological xylitol production by glucose during culture of *Candida guilliermondii* in sugarcane bagasse hydrolysate, *Braz Arch Biol Technol*, **50** (2007) 207-215.
- 160 Rivas B, Torre P, Domínguez J M, Converti A & Parajó J C, Purification of xylitol obtained by fermentation of corncob hydrolysates, *J Agri Food Chem*, **54** (2006) 4430-4435.
- 161 Duarte L C, Carvalho F, Lopes S, Marques S, Parajó J C & Gírio F M, Comparison of two posthydrolysis processes of brewery's spent grain autohydrolysis liquor to produce a pentose-containing culture medium, *Appl Biochem Biotechnol*, **113-116** (2004) 1041-1058.
- 162 Carvalho F, Duarte L C, Medeiros R & Gírio F M, Xylitol production by *Debaryomyces hansenii* in brewery spent grain dilute-acid hydrolysate: effect of supplementation, *Biotechnol Lett*, **29** (2007) 1887-1891.
- 163 Duarte L C, Carvalho F, Lopes S, Neves I & Gírio F M, Yeast biomass production in brewery's spent grains hemicellulosic hydrolysate, *Appl Biochem Biotechnol*, **148** (2008) 119-129.
- 164 Pessoa A, Jr., Mancilha I M & Sato S, Cultivation of *Candida tropicalis* in sugar cane hemicellulosic hydrolysate for microbial protein production, *J Biotechnol*, **51** (1996) 83-88.
- 165 Saha B C, Hemicellulose bioconversion, *J Ind Microbiol Biotechnol*, **30** (2003) 279-291.
- 166 Mielenz J R, Ethanol production from biomass: technology and commercialization status, *Curr Opin Microbiol*, **4** (2001) 324-329.
- 167 Nascimento R P, Coelho R R R, Marques S, Alves L, Gírio F M, Bon E P S & Amaral-Collaco M T, Production and partial characterisation of xylanase from *Streptomyces* sp. strain AMT-3 isolated from Brazilian cerrado soil, *Enzyme Microbiol Technol*, **31** (2002) 549-555.
- 168 Garrote G, Domínguez H & Parajó J C, Generation of xylose solutions from *Eucalyptus globulus* wood by autohydrolysis-posthydrolysis processes: Posthydrolysis kinetics, *Biores Technol*, **79** (2001) 155-164.
- 169 Garrote G, Domínguez H & Parajó J C, Manufacture of xylose-based fermentation media from corncobs by posthydrolysis of autohydrolysis liquors, *Appl Biochem Biotechnol*, **95** (2001) 195-207.

- 170 Boussaid A, Cai Y J, Robinson J, Gregg D J, Nguyen Q & Saddler J N, Sugar recovery and fermentability of hemicellulose hydrolysates from steam-exploded softwoods containing bark, *Biotechnol Prog*, **17** (2001) 887-892.
- 171 Duarte L C, Silva-Fernandes T, Carvalho F & Gírio F M, Dilute acid hydrolysis of wheat straw oligosaccharides, in press (2009) .
- 172 Puls J, Poutanen K, Körner H U & Viikari L, Biotechnical utilization of wood carbohydrates after steaming pretreatment, *Appl Microbiol Biotechnol*, **22** (1985) 416-423.
- 173 Belkacemi K, Turcotte G & Savoie P, Aqueous/steam-fractionated agricultural residues as substrates for ethanol production, *Ind Eng Chem Res*, **41** (2002) 173-179.
- 174 Vázquez M J, Alonso J L, Domínguez H & Parajó J C, Production of xylose-containing fermentation media by enzymatic post-hydrolysis of oligomers produced by corn cob autohydrolysis, *World J Microbiol Biotechnol*, **17** (2001) 817-822.
- 175 Vázquez M J, Alonso J L, Domínguez H & Parajó J C, Enzymatic processing of crude, xylooligomer solutions obtained by autohydrolysis of *Eucalyptus* wood, *Food Biotechnol*, **16** (2002) 91-105.
- 176 Kabel M A, Carvalho F, Garrote G, Avgerinos E, Koukios E, Parajó J C, Gírio F M, Schols H A & Voragen A G J, Hydrothermally treated xylan rich by-products yield different classes of xylo-oligosaccharides, *Carbohydr Polym*, **50** (2002) 47-56.
- 177 Beldman G, Hennekam J & Voragen A G J, Enzymatic hydrolysis of beer brewers' spent grain and the influence of pretreatments, *Biotechnol Bioeng*, **30** (1987) 668-671.
- 178 Faulds C B, Zanichelli D, Crepin V F, Connerton I F, Juge N, Bhat M K & Waldron K W, Specificity of feruloyl esterases for water-extractable and water-unextractable feruloylated polysaccharides: influence of xylanase, *J Cereal Sci*, **38** (2003) 281-288.
- 179 Puls J & Poutanen K, Mechanisms of enzymic hydrolysis of hemicelluloses (xylans) and procedures for determination of the enzyme activities involved, in *Enzyme Systems for Lignocellulosic Degradation*, edited by M P Coughlan (Elsevier Applied Science, London) 1989, 151-165.
- 180 Li K C, Azadi P, Collins R, Tolan J, Kim J S & Eriksson K E L, Relationships between activities of xylanases and xylan structures, *Enzyme Microbiol Technol*, **27** (2000) 89-94.
- 181 Hörmeyer H F, Bonn G, Kim D W & Bobleter O, Enzymatic saccharification of cellulosic materials after hydrothermolysis and organosolv pretreatments, *J Wood Chem Technol*, **7** (1987) 269-283.
- 182 Dekker R F H, Inhibitors of *Trichoderma reesei* b-glucosidase activity derived from autohydrolysis exploded *Eucalyptus regnans*, *Appl Microbiol Biotechnol*, **29** (1988) 593-598.
- 183 Cantarella M, Cantarella L, Gallifuoco A, Spera A & Alfani F, Effect of inhibitors released during steam-explosion treatment of poplar wood on subsequent enzymatic hydrolysis and SSF, *Biotechnol Prog*, **20** (2004) 200-206.
- 184 Zahedifar M, *Novel uses of lignin and hemicellulosic sugars from acid-hydrolysis lignocellulosic materials*, Ph D Thesis, University of Aberdeen, 1996.
- 185 van Zyl C, Prior B A & du Preez J C, Production of ethanol from sugar cane bagasse hemicellulose hydrolysate by *Pichia stipitis*, *Appl Biochem Biotechnol*, **17** (1988) 357-370.
- 186 Rodrigues D C G A, Silva S S & Felipe M G A, Fed-batch culture of *Candida guilliermondii* FTI 20037 for xylitol production from sugar cane bagasse hydrolysate, *Lett Appl Microbiol*, **29** (1999) 359-363.
- 187 Rodrigues D C G A, Silva S S, Prata A M R & Felipe M G A, Biotechnological production of xylitol from agroindustrial residues - Evaluation of bioprocesses, *Appl Biochem Biotechnol*, **70-72** (1998) 869-875.
- 188 Cruz J M, Domínguez J M, Domínguez H & Parajó J C, Antioxidant and antimicrobial effects of extracts from hydrolysates of lignocellulosic materials, *J Agri Food Chem*, **49** (2001) 2459-2464.
- 189 Roberto I C, Mancilha I M, Souza C A, Felipe M G A, Sato S & Castro H F, Evaluation of rice straw hemicellulose hydrolysate in the production of xylitol by *Candida guilliermondii*, *Biotechnol Lett*, **16** (1994) 1211-1216.
- 190 Perego P, Converti A, Palazzi E, Del Borghi M & Ferraiolo G, Fermentation of hardwood hemicellulose hydrolysate by *Pachysolen tannophilus*, *Candida shehatae* and *Pichia stipitis*, *J Ind Microbiol*, **6** (1990) 157-164.
- 191 Ranatunga T D, Jervis J, Helm R F, McMillan J D & Hatzis C, Toxicity of hardwood extractives toward *Saccharomyces cerevisiae* glucose fermentation, *Biotechnol Lett*, **19** (1997) 1125-1127.
- 192 Ferrari M D, Neirotti E, Albornoz C & Saucedo E, Ethanol production from *Eucalyptus* wood hemicellulose hydrolysate by *Pichia stipitis*, *Biotechnol Bioeng*, **40** (1992) 753-759.
- 193 Parajó J C, Alonso J L & Santos V, Kinetics of *Eucalyptus* Wood Fractionation in Acetic Acid-HCl-Water Media, *Biores Technol*, **51** (1995) 153-162.
- 194 Canettieri E V, Silva J B & Felipe M G A, Application of factorial design to the study of xylitol production from *eucalyptus* hemicellulosic hydrolysate, *Appl Biochem Biotechnol*, **94** (2001) 159-168.
- 195 Wilson J J, Deschatelets L & Nishikawa N K, Comparative fermentability of enzymatic and acid hydrolysates of steam-pretreated aspenwood hemicellulose by *Pichia stipitis* CBS 5776, *Appl Microbiol Biotechnol*, **31** (1989) 592-596.
- 196 Parekh S R, Parekh R S & Wayman M, Fermentation of wood-derived acid hydrolysates in a batch bioreactor and in a continuous dynamic immobilized cell bioreactor by *Pichia stipitis*, *Process Biochem*, **22** (1987) 85-91.
- 197 Taherzadeh M J, Niklasson C & Lidén G, Conversion of dilute-acid hydrolyzates of spruce and birch to ethanol by fed-batch fermentation, *Biores Technol*, **69** (1999) 59-66.
- 198 Millati R, Niklasson C & Taherzadeh M J, Effect of pH, time and temperature of overliming on detoxification of dilute-acid hydrolyzates for fermentation by *Saccharomyces cerevisiae*, *Process Biochem*, **38** (2002) 515-522.
- 199 Schell D J, Ruth M F & Tucker M P, Modeling the enzymatic hydrolysis of dilute-acid pretreated douglas fir, *Appl Biochem Biotechnol*, **77-79** (1999) 67-81.
- 200 Tenkanen M, Pentosan-acting enzymes, in *Biomass derived Pentoses*, edited by M J O'Donohue (INRA, Reims) 2006, 15.